

MECHANICAL PROPERTIES OF HYBRID POLYMER COMPOSITES WITH BAMBOO AND E-GLASS FIBER PRODUCED BY HAND LAY-UP PROCESS

Faisal Gulzar¹, Danish Ahmad Reshi², Zahid Ahmad Rather³

^{1,2&3}Plant Engineer, Abraaq Agro Fresh LLP Industrial Growth Centre Lassipora, Pulwama

Abstract - Reinforced with natural fibers such as jute, bamboo, linen, sisal, hemp, and the coir has become increasingly important. Natural fiber, commonly used in most parts of the world, requires minimal financial input and maintenance. Environmentally friendly and economical for polymer composites reinforced with synthetic fibers. However, composites reinforced with natural fibers have low water absorption and may not meet the requirements of specific applications. Due to this problem, natural fibers can be combined with synthetic fibers having the same matrix material to obtain the greatest advantage in improving its properties. In this case, hybrid composites made from natural fiber and fiber-reinforced polymer composites are very important for current needs. This article discusses the mechanical properties of bidirectional bamboo reinforced fibers and epoxy hybrid composite elements. Mechanical properties such as impact strength, flexural strength, and moisture absorption are evaluated experimentally following ASTM standards.

Key Words: bamboo, fiberglass, epoxy.

1. INTRODUCTION

The worldwide interest for wood as a structural material is consistently developing, while the accessibility of this common asset is decreasing. This circumstance has prompted the advancement of elective materials. Of the different engineered materials that have been investigated and supported, polymer composites guarantee significant cooperation as building materials. There has been a developing enthusiasm for using common strands as a fortification in polymer composite for making ease development materials as of late. Characteristic filaments are imminent strengthening materials and their utilization as of not long ago has been more conventional than specialized. They have since a long time ago filled numerous valuable needs however the use of the material innovation for the use of normal filaments as a fortification in polymer network occurred in nearly late years. Financial and other related factors in many creating nations where regular strands are rich interest that researchers and specialists apply fitting innovation to use these normal filaments as adequately and monetarily as conceivable to deliver great quality fiber fortified polymer composites for lodging and different needs. Among the different common strands, bamboo is exceptionally compelling in that its composites have high effect quality other than having moderate elastic and flexural properties contrasted with different lignocelluloses filaments. The characteristic assets of the World are draining

quickly because of the high pace of abuse and the low pace of rebuilding, prompting an expansion in an Earth-wide temperature boost and contamination risks. Lately, there has been expanding enthusiasm for the substitution of manufactured filaments in strengthened plastic composites by common plant strands, for example, jute, coir, flax, hemp, and sisal. Bamboo is one of the common filaments broadly accessible in many pieces of the world; it requires the least money related information and upkeep for development and is frequently developed in badlands, which helps in soil preservation. Focal points of bamboo fiber are low thickness and high explicit quality, biodegradable and inexhaustible assets, and it gives warm and acoustic protection. Bamboo fiber is better than other common strands, for example, jute from multiple points of view, including its higher quality, splendid gleaming shading, huge staple length, poor pleat property, variety in properties and quality because of the developing conditions, constrained most extreme preparing temperatures.

2. EXPERIMENTATION

2.1. Materials

2.1.1. Bamboo

Bamboos remember probably the quickest developing plants for the world, because of an interesting rhizome subordinate System. Certain types of bamboo can develop 91cm (36 inches) inside a 24-hour time frame. Goliath bamboos are the biggest individuals from the grass family. Bamboo has a higher explicit compressive quality than wood, block, or cement Furthermore, a particular rigidity that adversaries steel.



Fig. 1: Bamboo fiber

2.1.2 Extraction of bamboo

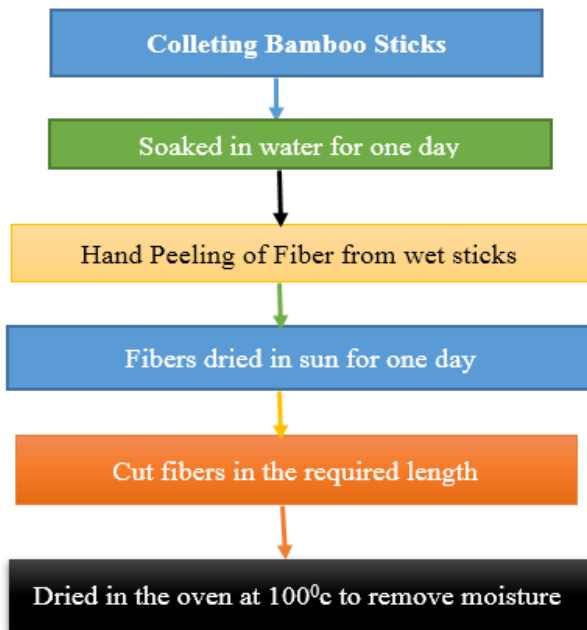


Fig 2: Extraction of bamboo

2.1.3. Glass

Glass filaments are the most well-known of all strengthening strands for (plastic) network composites. The head focal points of glass fiber are ease, high rigidity, high compound resistance, and fantastic protecting properties. The two kinds of glass strands normally utilized in the fiber-reinforced plastic enterprises are glass and S - Glass, another sort known as C-Glass is utilized in chemical applications requiring more noteworthy erosion protection from acids than is given by E - Glass



Fig 3: E-glass fiber

2.1.4. Epoxy Resin

Epoxy or poly-iodide is a thermosetting epoxide polymer that fixes (polymers and cross-connections) When blended in with catalyzing specialist or "hardener". Epoxy gum and added substances add to the thickness of the framework and the contracting attributes. The measure of the fillers and diluents will affect both the physical and taking care of the properties of the pitch framework.

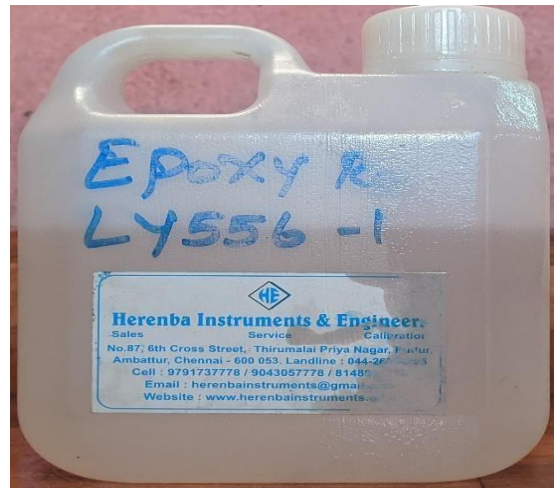


Fig 4(a) Epoxy resin



Fig 4(b) Hardener

2.1.5. Hardener

Epoxy hardeners are not impetuses and they respond with the epoxy pitches, extraordinarily adding to a definitive property of the relieved epoxy tar framework. Epoxy hardeners give gel time, blended consistency, de-form time of the epoxy pitch system. Physical properties of the epoxy tar frameworks, for example, ductile, pressure, flexural properties, and so forth. are likewise affected by epoxy hardeners. The presentation of epoxy hardeners in the epoxy pitch framework relies upon the compound qualities while applying the epoxy pitches framework.

2.2. Preparation of composites

The framework of unsaturated polyester and monomer of styrene are blended in the proportion of 100:25 parts by weight separately. Later the added substance glass is blended completely and afterward the quickening agent of methyl ethylketone peroxide 1% by weight and impetus of Cobalt Naphthenate of 1% by weight were added to the blend and blended all together. Right now composites were set up by hand lay-up strategy, the discharging specialist of silicon is splashed to glass form and the network blend is poured into the shape. The fiber is added to the lattice blend, which was poured in the glass form. The overabundance pitch was expelled from the form and the glass plate was set on top. The castings were permitted to remedy for 24hrs at room temperature and afterward throwing is set at a temperature of 80°C for 4 hrs. The composite is discharged from the shape and is sliced to get ready test examples.

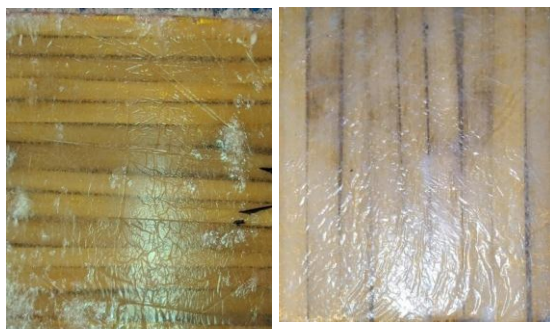


Fig5: Bamboo fiber composites

1. RESULTS AND DISCUSSION

3.1 Izod Test

A pendulum-type single blow impact test in which the specimen, usually notched, is fixed at one end and free at another end. The specimen is broken by a falling pendulum. The energy absorbed as measured by the subsequent rise of the pendulum is a measure of impact strength or notch toughness.

Toughness: The ability of the material to absorb energy and deform plastically before fracture. It is usually measured by the energy absorbed in a notched impact test like Charpy and Izod tests. The area under the stress-strain curve in a tensile test is also a measure of toughness and as such is proportional to the combined effects of tensile strength and ductility.

The Izod impact energy (I) i.e, the energy required to break the specimen is obtained directly from the test. The depth below the notch and the breadth of the specimen are measured (i.e d and b). The effective cross-sectional area below the impact strength

Table 1: Impact Test Readings

	Material	Initial reading in J	Final reading in J	Energy Absorbed = k1 - k2	Izod impact strength I=K/A
1	Specimen1	170	130	40	400
2	Specimen2	170	118	52	520

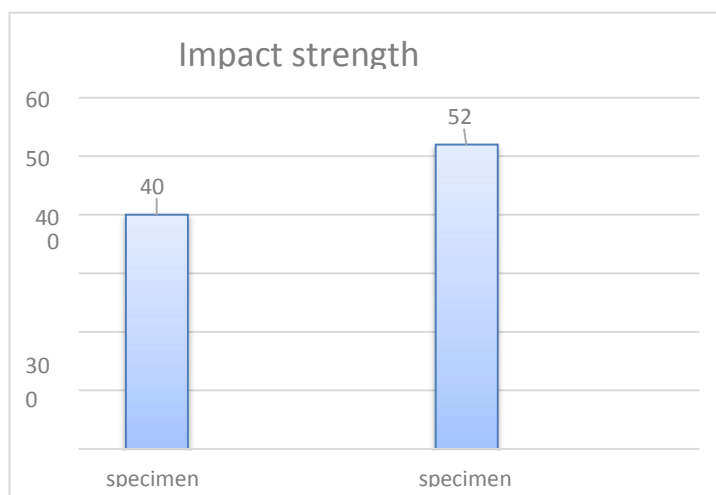


Fig 6: Impact Izod Test

3.2 Flexural test

The action of Bending or curving is called Flexure. Flexural strength is the maximum resistance of a material in bending. This is typically applicable for structural elements whose behavior can be reflected by beams. Flexural strength is expressed in terms of modulus of rupture (MOR) in Mpa or Pa. The flexural strength is a commonly used in the design of rigid pavements.

Table 2: Flexural Test Readings

S.No	Materials	Peak load (KN)	Flexural modulus in Mpa	Flexural strength (N/mm ²)
1	Specimen 1	3.47	102.5	32.71
2	Specimen-2	4.12	123.92	41.20

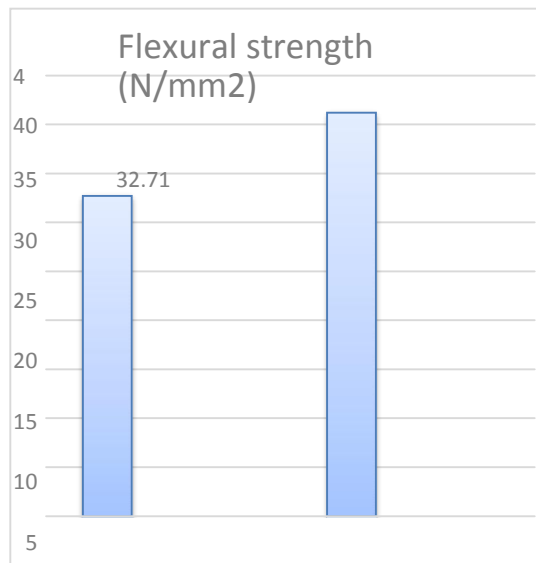


Fig 7: Flexural strength (N/mm²)

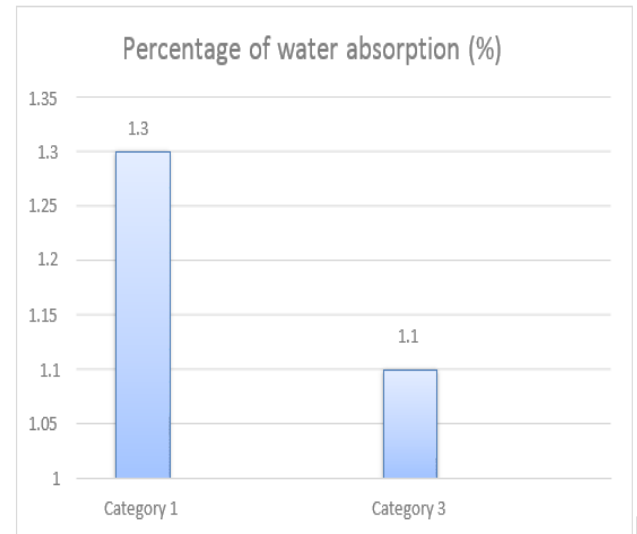


Fig8: Percentage of water absorption

3.3 Water absorption test

Water Absorption 24 Hour/Equilibrium ASTM D570 Water absorption is used to determine the amount of water absorbed under specified conditions. Factors affecting water absorption include the type of plastic, additives used, temperature and length of exposure. The data sheds light on the performance of the materials in water or humid environments.

Percent Water Absorption = $\frac{[(\text{Wet weight} - \text{Dry weight}) / \text{Dry weight}] \times 100}{\text{Size of specimen} = 300 \times 200 \text{ mm}}$

Table 3: Water Absorption Readings

S.No	Material	Amount of Water Absorbed (g)	Percentage of Water Absorbed (%)
1	Category - 1	0.23	1.3
2	Category- 2	0.18	1.1

Conclusion

The use of bamboo fiber as a reinforcing agent in polymer-based composites was reviewed from viewpoints of status and future expectations of natural fibers in general, structure and properties of bamboo fiber, fiber surface modifications, and physical and mechanical properties of bamboo fiber-based polymer composites. Bamboo fibers have good potential as reinforcements in polymer (thermoplastics, thermoset, and rubbers) composites. Due to the low density and high specific properties of bamboo fibers, composites based on these fibers may have very good implications in the automotive and transportation industry. However, suitable cost-effective design and fabrication techniques for manufacture should be developed. Bamboo fiber polymer composites with and without hybridization should be developed and characterized to arrive at a series of composites that may find use in several areas such as marine, structural, consumer articles and industrial applications.

References

- 1) Chawla K. K. Composite Materials: Science and Engineering: Springer, 1998.
- 2) Krevelen D.W. Properties of Polymers: Their correlation with chemical structure; their numerical estimation and prediction from additive group contributions: Elsevier, 2009.
- 3) Kutz M. Mechanical Engineers Handbook, Third Edition, John Wiley and Sons Inc., Hoboken, New Jersey, 2000.
- 4) Ashby M. F. Engineering materials and processes: Desk Reference.
- 5) Malik P. K. Fiber-reinforced Composites: Materials, Manufacturing, and Design.

- 6) Chandra R, Singh S. P, Gupta K. Damping studies in Fiber reinforced composites: A review, pp. 41-51.
- 7) Malik P. K. Fiber-reinforced Composites: Materials, Manufacturing, and Design. 8. Lubin G. Handbook of Composites.
- 8) Kelleher P. G. Reinforced Thermoplastics: composition, processing and applications, 1993. 10. Biswas S, Satpathy A, A review on the natural fiber composites and their erosion wear characteristics.
- 9) Nabi Sahib D, Jog J. P, natural fiber polymer composites: A review, *Advances in polymer technology*, 18(4), (2004), pp 351-363. Mechanical Engineering Department, N.I.T. Rourkela Page 35
- 10) Kozłowski R and W-Pryzbylak M use of natural fiber reinforced plastics, Institute of Natural Fibers, Poznan, Poland.
- 11) Kushwaha K. P and Kumar R, Bamboo fiber reinforced thermosetting resin composites: Effect of graft polymerization of fiber with Methacrylamide, *Journal of applied polymer science*, 118, (2010), pp 1006-1013.
- 12) Samal S. K, Mohanty S, Nayak S. K, Polypropylene-Bamboo/Glass Fiber Hybrid Composites: Fabrication and analysis of mechanical, morphological, thermal and dynamic mechanical behavior. Central Institute of Plastic Engineering and Technology, Bhubaneswar.
- 13) Kalaprasad G, Joseph K. and Thomas S. Influence of short glass fiber addition on the mechanical properties of banana reinforced LDPE composites, *J. Comp. Matter*, 31: (1997), pp 509-526.
- 14) Kalaprasad G, Thomas S, Pavithran C, Neelakantan N. R. and Balakrishna S. Hybrid effect in the mechanical properties of short banana-glass hybrid fiber reinforced LDPE composites, *J. Reinf. Plast Compo*, 15, (1996), pp 48- 73.
- 15) Yang G. C, Zeng H. M, Jian, N. B and Li, J. J. Properties of banana/ glass fiber reinforced PVC hybrid composites. *Plastics Industry*, 1: (1996), pp 79-81.
- 16) Satyanarayana K. G, Sukumaran K, Mukherjee P. S, Pavithran C and Pillai S. G. K, "Natural Fiber-Polymer Composites", *Journal of Cement and Concrete Composites*, 12(2), 1990, pp. 117-136.
- 17) Satyanarayana K. G, Sukumaran K, Kulkarni A. G, Pillai S. G. K, and Rohatgi P. K, "Fabrication and Properties of Natural Fiber-Reinforced Polyester Composites", *Journal of Composites*, 17(4), 1986, pp. 329-333. Mechanical Engineering Department, N.I.T. Rourkela Page 36
- 18) Mansur M. A and Aziz M. A, "Study of Bamboo-Mesh Reinforced Cement Composites" *Int. Cement Composites and Lightweight Concrete*", 5(3), 1983, pp. 165-171.
- 19) Gowda T. M, Naidu A. C. B, and Chhaya R, "Some Mechanical Properties of Untreated Jute Fabric-Reinforced Polyester Composites", *Journal of Composites Part A: Applied Science and Manufacturing*, 30(3), 1999, pp. 277- 284.
- 20) Karmaker AC, the effect of water absorption on dimensional stability and impact energy of jute reinforced polypropylene. *J Mat Sci Lett* 1997;16:462-464.
- 21) Katz HS, Milewski JV, editors, *Handbook for fillers for Plastics*. New York; Van Nostrand Reinhold, 1987.